

Document downloaded from:

<http://hdl.handle.net/10251/48118>

This paper must be cited as:

Vilaplana Cerda, RI.; Santamaría-Pérez, D.; Gomis Hilario, O.; Manjón Herrera, FJ.; González, J.; Segura, A.; Muñoz, A.... (2011). Structural and vibrational study of Bi₂Se₃ under high pressure. *Physical Review B*. 84:184110-1-184110-15.
doi:10.1103/PhysRevB.84.184110.



The final publication is available at

<http://journals.aps.org/prb/pdf/10.1103/PhysRevB.84.184110>

Copyright American Physical Society

Structural and vibrational study of Bi₂Se₃ under high pressure

R. Vilaplana,^{1,*} D. Santamaría-Pérez,² O. Gomis,¹ F.J. Manjón,³ J. González,^{4,5}
A. Segura,⁶ A. Muñoz,⁷ P. Rodríguez-Hernández,⁷ E. Pérez-González,⁷ V.
Marín-Borrás,⁸ V. Muñoz-Sanjose,⁸ C. Drasar,⁹ and V. Kucek⁹

¹ Centro de Tecnologías Físicas, MALTA Consolider Team, Universitat Politècnica de
València, 46022 Valencia (Spain)

² Departamento de Química Física I, Universidad Complutense de Madrid, MALTA Consolider
Team, Avenida Complutense s/n, 28040 Madrid, Spain

³ Instituto de Diseño para la Fabricación y Producción Automatizada, MALTA Consolider
Team, Universitat Politècnica de València, 46022 Valencia (Spain)

⁴ DCITIMAC - MALTA Consolider Team, Universidad de Cantabria, Santander (Spain)

⁵ Centro de Estudios de Semiconductores, Universidad de los Andes, Mérida 5201 (Venezuela)

⁶ Instituto de Ciencia de Materiales de la Universidad de Valencia - MALTA Consolider Team -
Departamento de Física Aplicada, Universitat de València, 46100 Burjassot, Valencia (Spain)

⁷ MALTA Consolider Team - Departamento de Física Fundamental II, Instituto Univ. de Materiales y
Nanotecnología, Universidad de La Laguna, La Laguna, Tenerife (Spain)

⁸ Departamento de Física Aplicada, Universitat de València, 46100 Burjassot, Valencia (Spain)

⁹ Faculty of Chemical Technology, Department of Physics, University of Pardubice,
Studentská 95, 53210-Pardubice, (Czech Republic)

Correspondence and request for materials should be addressed to R. Vilaplana


(rovilap@fis.upv.es)

Supplementary materials

* Corresponding author. E-mail address: rovilap@fis.upv.es
Tel.: + 34 96 652 84 26, Fax: + 34 96 652 84 09


Supplementary Figure 1.

Raman spectrum of β -Bi₂Se₃ at 13.5 GPa and the corresponding fit of Voigt profiles corresponding to the Raman-active modes of the C2/m structure.

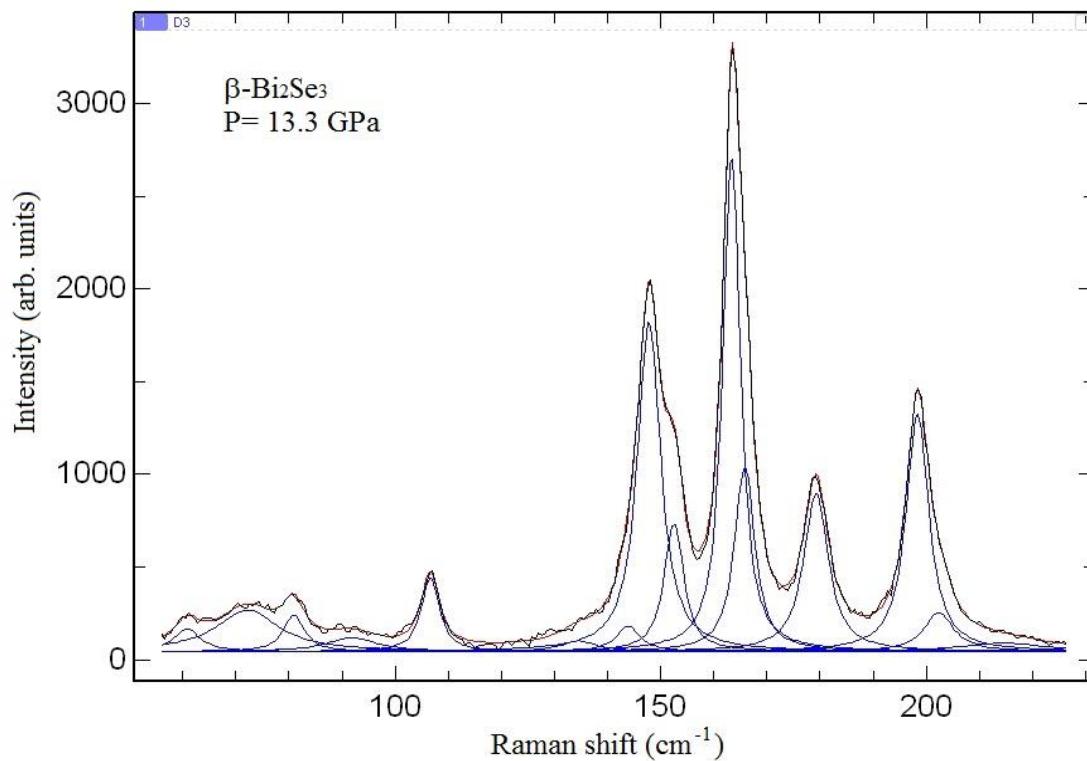

Supplementary Figure 2.

Raman spectrum of γ -Bi₂Se₃ at 19.9 GPa and the corresponding fit of Voigt profiles corresponding to the Raman-active modes of the C2/c structure.

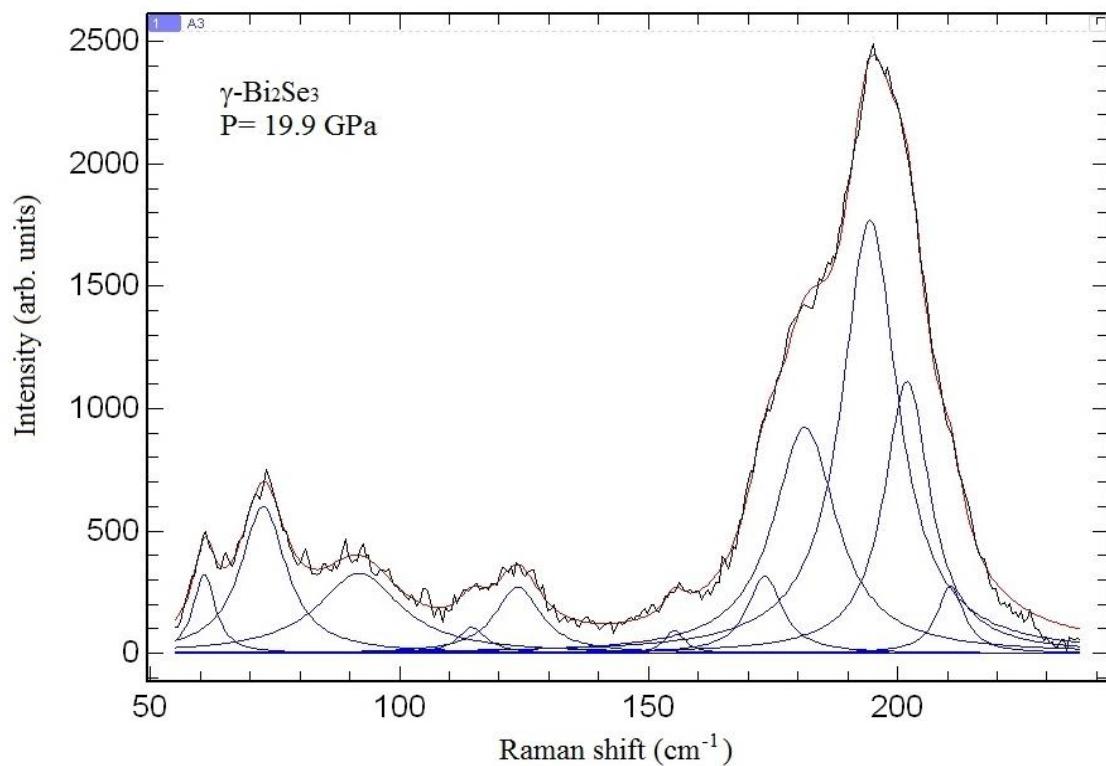

Supplementary Table I. Theoretical (th.) *ab initio* IR-mode frequencies and pressure coefficients in $\alpha\text{-Bi}_2\text{Se}_3$ (R-3m phase) at room temperature and $P_0 = 1$ atm, as obtained from fits to the data using $\omega(P) = \omega(P_0) + a_1 \cdot (P - P_0)$. Experimental (exp.) and theoretical IR-mode frequencies at room pressure of other works are given for comparison.

Mode	$\omega_0(\text{th.})$ (cm ⁻¹)	$a_1(\text{th.})$ (cm ⁻¹ /GPa)	$\omega_0(\text{th.})$ (cm ⁻¹)	$\omega_0(\text{th.})$ (cm ⁻¹)	$\omega_0(\text{exp.})$ (cm ⁻¹)	$\omega_0(\text{exp.})$ (cm ⁻¹)
E_u^1	80.3	3.29	64.69	85.1	65	61
E_u^2	129.9	1.44	126.8	133.0	129	133
A_{2u}^1	137.3	2.22	136.7	142.7		
A_{2u}^2	159.8	1.77	155.5	167.1		
Ref.	This work ^a	This work ^a	1 ^a	1 ^b	2	3

^a GGA calculations including the spin-orbit coupling.

^b GGA calculations without the spin-orbit coupling.

It can be observed that the room pressure frequencies of our calculations, which include the spin-orbit coupling using GGA-PBEsol for the exchange-correlation term, compare reasonably well with the experimental values already published and are intermediate between the theoretical results, obtained using GGA with and without spin-orbit coupling (see Ref. 1).

Supplementary Table II. Theoretical (th.) *ab initio* IR-mode frequencies and pressure coefficients observed in $\beta\text{-Bi}_2\text{Se}_3$ (C2/m phase) at room temperature at $P_0 = 9.8$ GPa as obtained from fits using $\omega(P) = \omega(P_0) + a_1 \cdot (P - P_0)$. No spin-orbit coupling is included.

Mode	$\omega(P_0)$ (th.) (cm ⁻¹)	a_1 (th.) (cm ⁻¹ /GPa)
B_u^1	52.1	1.02
A_u^1	56.6	0.84
B_u^2	88.3	1.42
A_u^2	108.3	1.47
B_u^3	114.7	1.54
B_u^4	129.0	1.50
A_u^3	138.9	0.55
B_u^5	160.4	1.42
A_u^4	164.6	1.15
B_u^6	167.3	1.44
B_u^7	180.0	1.65
B_u^8	192.7	1.98

Supplementary Table III. Theoretical (th.) *ab initio* IR-mode frequencies and pressure coefficients observed in $\gamma\text{-Bi}_2\text{Se}_3$ (C2/c phase) at room temperature at $P_0 = 19.9$ GPa as obtained from fits using $\omega(P) = \omega(P_0) + a_1 \cdot (P - P_0)$. No spin-orbit coupling is included.

Mode	$\omega(P_0)$ (th.) (cm ⁻¹)	a_1 (th.) (cm ⁻¹ /GPa)
A_u^1	57.0	0.51
B_u^1	66.5	0.15
A_u^2	83.4	0.68
A_u^3	121.6	0.11
B_u^2	127.8	-0.09
B_u^3	136.8	2.12
A_u^4	138.5	2.22
B_u^4	142.2	2.32
B_u^5	170.6	1.54
B_u^6	174.4	2.66
A_u^5	185.1	2.34
A_u^6	203.5	1.04

References:

- [1] W. Cheng and S.F. Ren, Phys. Rev. B **83**, 094301 (2011).
- [2] W. Richter, H. Köhler, and C.R. Becker, Phys. Stat. Solidi b **84**, 619 (1977).
- [3] A.D. LaForge, A. Frenzel, B.C. Pursley, T. Lin, X. Liu, J. Shi, and C.N. Basov, Phys. Rev. B **81**, 125120 (2010).